

## Off-Specular Neutron Reflection from Magnetic Media with Nondiagonal Reflectivity Matrices

Dmitri K. Korneev, Victor I. Bodnarchuk, \*Vladimir K. Ignatovich

*Laboratory of neutron physics, JINR, 141980 Dubna Moscow reg., Russia.*

(Received 21 February 1996; accepted 12 April 1996)

The reflection of neutrons from magnetic substances is described using the reflection matrix with nondiagonal, in general, matrix elements which determine neutron spin reversal. In external field the spin reversal is accompanied by changes of the neutron kinetic energy and reflection angle. The particular case of reflection from a magnetic mirror with magnetization noncollinear to the external field is considered. The probability of spin reversal and a deviation of reflection angles from the specular one are calculated. The experiment to observe this effect is described and its results are reported.

KEYWORDS: thermal neutrons, magnetic scattering, polarization, optical potential

### §.1 Introduction

Since the time of the first works by Hughes and Burgoy<sup>1)</sup>, specular reflection has been used to polarize neutrons. With polarized neutrons one can investigate, for instance, magnetization profiles of films and multilayered systems.<sup>2-6)</sup> It was pointed out<sup>7-13)</sup> that reflection from films with noncollinear magnetic structures is more complicated than reflection from films with collinear ones. In the noncollinear case the reflection is characterized by the reflection matrix:

$$\hat{R} = \begin{pmatrix} R_{++} & R_{+-} \\ R_{-+} & R_{--} \end{pmatrix}$$

with nonzero elements  $R_{+-}$  and  $R_{-+}$ . To measure all matrix elements in  $\hat{R}$  is the main goal of polarized neutron reflectometry.

In the next section, the angular characteristics of reflection with spin-flip in external fields are considered. In the third section, the matrix elements of  $\hat{R}$  and the intensities of constituent beams for the case of reflection from a magnetic mirror with magnetization noncollinear to the external field are calculated. In the fourth section, the experiment to observe off-specular reflection is described.

### §.2 Angular splitting of the reflected beam

The reflection of neutrons from an interface in an external magnetic field can be off-specular (though coherent) if it is accompanied by spin flipping. In general, the incident beam after reflection undergoes triple splitting, as shown in Fig. 1. It contains the middle part which is specular and two side lobes which are off-specular and perfectly polarized. The intensity of the side lobes are determined by the matrix elements  $R_{+-}$  and  $R_{-+}$  of the matrix  $\hat{R}$  and by the incident beam polarization. If the incident beam is perfectly polarized, one of the side lobes vanishes. If the incident beam is nonpolarized, two side beams in weak external fields have almost equal intensities. The splitting of the beam takes place because

of spin flipping, energy conservation, and the conservation of components of neutron momentum parallel to the interface.

Let us denote  $\mathbf{k} = (k_{\parallel}, k_{\perp})$  the wave vector of the incident neutron with  $k_{\perp}$  and  $k_{\parallel}$  being its normal and parallel to surface components. In the external field  $B$  the neutron has the potential energy  $-\sigma B$ , where  $B$  is measured in  $\hbar^2 / 2m\mu$  ( $m, \mu$  are the neutron mass and magnetic moment, respectively) and  $\sigma$  are the Pauli matrices. On spin reversal the potential energy changes in magnitude by  $\pm 2B$ . Because of energy conservation it changes the kinetic energy:  $k^2 \rightarrow k^2 \pm 2B$ . In the reflection from an interface the components  $k_{\parallel}$  are also conserved. Thus the change of the kinetic energy means a change in the normal component  $k_{\perp}$ :  $k_{\perp} \rightarrow k_{\perp}^{\pm} = \sqrt{k_{\perp}^2 \pm 2B}$ , and as a result a subsequent change in the reflection angle. It is not difficult to calculate the angular deviation of shifted beams. For a small grazing angle  $\phi_0 = 10^{-2} - 10^{-3}$  rad we have

$$\begin{aligned} \frac{\Delta\phi^{\pm}}{\phi_0} &= \frac{\Delta k_{\perp}^{\pm}}{k_{\perp}} = \sqrt{1 \pm 2B/k_{\perp}^2} - 1 \\ &= \sqrt{1 \pm 1.47 \cdot 10^{-10} B \lambda^2 / \phi_0^2} - 1 \end{aligned}$$

Here the neutron wave length  $\lambda$  is measured in  $\text{\AA}$ ,  $B$  in

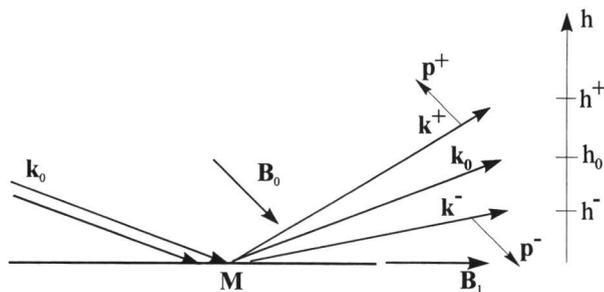


Fig.1 Following the reflection from a magnetized mirror with the magnetization  $M$  noncollinear to the external magnetic field  $B_0$  the nonpolarized incident neutron beam with a wave vector  $k_0$  splits into three beams. Two off-specular beams with the wave vectors  $k^+$  and  $k^-$  are ideally polarized. The splitting of the beam gives the distribution over height  $h$  of the reflected neutrons.

Present address: Research Reactor Institute Kyoto University Kumatori-cho, Senan-gan, Osaka 590-04, Japan.

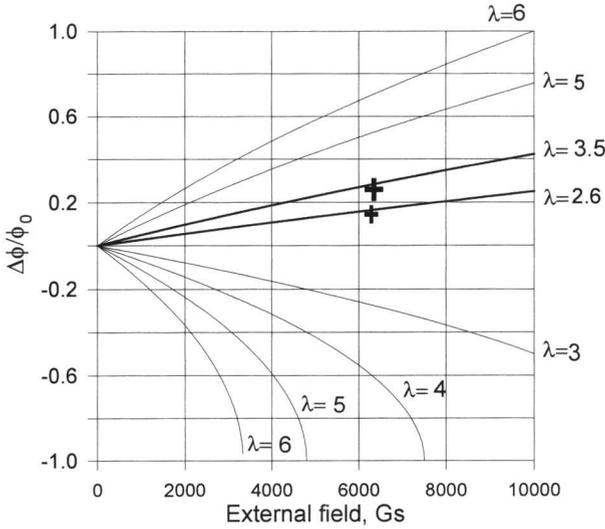


Fig.2 The relative angular splitting of spin reversed beams in dependence on  $\lambda$  (in Å) and the external magnetic field for  $\phi_0 = 4.2$  mrad. The crosses are the experimental points (see sec. 4).

gauss, and  $\phi_0$  --- in radians. The dependence of the relative splitting  $\Delta\phi^\pm/\phi_0$  on  $\lambda$  and  $B$  is shown in Fig. 2.

If the external field is sufficiently large, spin reversal is forbidden for  $\Delta\phi < 0$ .

### §.3 Matrix $\hat{R}$

Let us find the solution of the Schrödinger equation in the presence of the external magnetic field  $B_0$  and a magnetized reflecting mirror:

$$(\Delta - u\theta(z > 0) + \sigma B(z) + k^2)\varphi = 0 \quad (3.1)$$

where  $u$  is an optical potential of the mirror, which is supposed to fill the half space  $z > 0$ ,  $\theta$  is the step function equal to unity when the inequality in its argument is satisfied and to zero in the opposite case,

$$B(z) = B_0\theta(z < 0) + B_1\theta(z > 0),$$

and  $B_1$  is the magnetic induction of the mirror. We consider the case when  $B_0 \neq B_1$ .

The solution is  $\psi(\mathbf{r}) = \exp(i\mathbf{k}_\parallel \mathbf{r}_\parallel)\xi(z)$ , where

$$\begin{aligned} \xi(z) = & \theta(z < 0) \left[ \exp(i\hat{k}_\perp^+ z)\xi_0 + \exp(-i\hat{k}_\perp^+ z)\hat{R}_0\xi_0 \right] \\ & + \theta(z > 0) \exp(i\hat{k}_\perp^+ z)\hat{T}\xi_0 \end{aligned} \quad (3.2)$$

$\hat{R}$ ,  $\hat{T}$  are the reflection and transmission matrices,  $\hat{k}_\perp^\pm = \sqrt{k_\perp^2 \pm \sigma B}$ ,  $\hat{k}_\perp^\pm = \sqrt{k_\perp^2 - u \pm \sigma B}$ , and  $\xi$  is the spinor state of the incident particle. For simplicity in the following, we shall omit the subscript  $\perp$ .

Matching of wave function at the interface  $z=0$  for arbitrary  $\xi_0$  gives two equations for  $\hat{R}$  and  $\hat{T}$ :

$$\hat{I} + \hat{R} = \hat{T}, \hat{k}^+(\hat{I} - \hat{R}) = \hat{k}^{1+}.$$

The solution of these equations can be represented as follows:

$$\hat{R} = (\hat{k}^+ + \hat{k}^{1+})^{-1}(\hat{k}^+ - \hat{k}^{1+}),$$

$$\hat{T} = (\hat{k}^+ + \hat{k}^{1+})^{-1}2\hat{k}^+$$

Here we shall consider in details only the matrix  $\hat{R}$ .

It is possible to eliminate the matrices  $\sigma$  in the denominator by representing  $\hat{R}$  in the form

$$\hat{R} = (\hat{k}^- + \hat{k}^{1-})^{-1}(\hat{k}^- - \hat{k}^{1-})/N \equiv \hat{A}/N \quad (3.3)$$

where  $N$  is the number, and it is useful to calculate it as a matrix element:

$$N = \langle + | k^+ k^- + \hat{k}^{1+} \hat{k}^{1-} + \hat{k}^{1-} k^+ + k^- \hat{k}^{1+} | + \rangle,$$

where  $|\pm\rangle$  represent the eigen states of the matrix  $\sigma B_0$ :

$$\sigma B_0 |\pm\rangle = \pm |\pm\rangle.$$

Evaluation gives

$$\begin{aligned} N = & (k^+ + k^{1+})(k^- + k^{1-}) \\ & - (k^{1-} - k^{1+})(k^+ - k^-) \sin^2(\chi/2) \end{aligned} \quad (3.4)$$

where  $k^\pm = \sqrt{k^2 \pm B_0}$ ,  $k^{1\pm} = \sqrt{k^2 - u \pm B_1}$  are c-numbers now, and  $\chi$  is the angle between the vectors  $B_0$  and  $B_1$ .

The numerator of (3.2) can be reduced to the form:

$$\begin{aligned} \hat{A} = & k^- k^+ - k^{1-} k^{1+} + \hat{k}^- \hat{k}^{1+} - \hat{k}^{1-} \hat{k}^- \\ = & k^+ k^- - k^{1+} k^{1-} + (1/2)(k^{1-} + k^{1+})(\hat{k}^+ - \hat{k}^-) \\ & - (1/2)(k^{1+} - k^{1-})(\hat{k}^- \sigma b_1 + \sigma b_1 \hat{k}^+) \end{aligned}$$

where the first two terms do not contain the  $\sigma$  matrices at all, and  $b_1$  is the unit vector in the direction of  $B_1$ .

Now we can calculate the matrix elements of  $\hat{A}$ :

$$\begin{aligned} \langle \pm | \hat{A} | \pm \rangle = & (k^- \pm k^{1-})(k^+ \mp k^{1+}) \\ & \pm (k^{1+} - k^{1-})(k^+ + k^-) \sin^2(\chi/2) \\ \langle \pm | \hat{A} | \mp \rangle = & -(k^{1+} - k^{1-})k^\pm \sin \chi \end{aligned}$$

In the case of  $\chi$  (and the similarly for  $\chi = \pi$ ) the  $\hat{R}$  becomes diagonal with the elements  $R_+ = (k^- - k^{1-})/(k^+ + k^{1+})$ ,  $R_- = (k^+ - k^{1+})/(k^- + k^{1-})$ .

For the general case the final expressions for the matrix elements of  $\hat{R}$  are:

$$\begin{aligned} R_{\pm\pm} = & \frac{1}{C} \left\{ R_\pm \mp \frac{(k^{1+} - k^{1-})(k^+ + k^-)}{(k^- + k^{1-})(k^+ + k^{1+})} \sin^2(\chi/2) \right\} \\ R_{\pm\mp} = & \frac{1}{C} \left\{ - \frac{(k^{1+} - k^{1-})k^\mp}{(k^- + k^{1-})(k^+ + k^{1+})} \sin \chi \right\} \\ C = & 1 - \frac{(k^{1+} - k^{1-})(k^- - k^+)}{(k^- + k^{1-})(k^+ + k^{1+})} \sin^2(\chi/2) \end{aligned} \quad (3.5)$$

These formulas are useful in calculating the beam splitting, but the notations are not appropriate for an experiment,

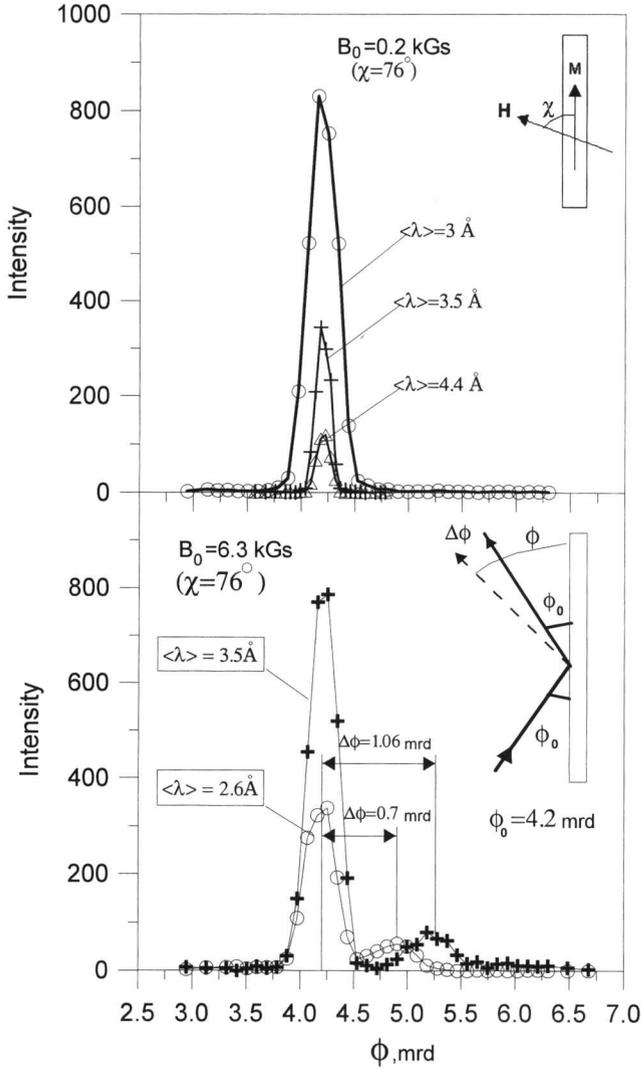


Fig.3 The dependence of the reflected neutron intensity on the angle  $\phi$  of detector positioning.

- a)  $B=0.2$  kGs,  $\chi=76^\circ$ , the detector aperture  $\delta\phi=0.18$  mrad, the grazing angle of the incident beam is  $\phi_0=4.2$  mrad. The intensity distribution maxima for different  $\lambda$  are observed at the same specular angle  $\phi = \phi_0$ .
- b)  $B=6.3$  kGs,  $\chi=76^\circ$ ,  $\delta\phi=0.18$  mrad,  $\phi_0=4.2$  mrad. The angular distribution of the reflected intensity for two different intervals of  $\lambda$ . In the vicinity of the specular beam ( $\phi = \phi_0$ ), off-specular ones appear. The angular shift  $\Delta\phi = \phi - \phi_0$  has the quadratic dependence on the averaged wavelength  $\langle\lambda\rangle$ .

because both spin states in the incident beam are characterized by the same wave vector  $\mathbf{k}^+ = \mathbf{k}^- = \mathbf{k}$  with a given normal component  $k$ . Thus, if we consider the splitting of the part of the beam initially polarized along the field, we must replace  $k^2 - B_0$  by  $k^2$  which means shifting of all  $k^2$  in (3.5) by  $B_0$ . Thus,  $k^+$  for that part of the beam becomes  $k^+ = \sqrt{k^2 + 2B_0}$  and

$k^{1\pm} = \sqrt{k^2 - u + B_0 \pm B_1}$ . For the part of the incident beam polarized in the opposite direction we must take  $k^+ \equiv k$  and then  $k^- = \sqrt{k^2 - 2B_0}$ , and

$$k^{1\pm} = \sqrt{k^2 - u - B_0 \pm B_1}.$$

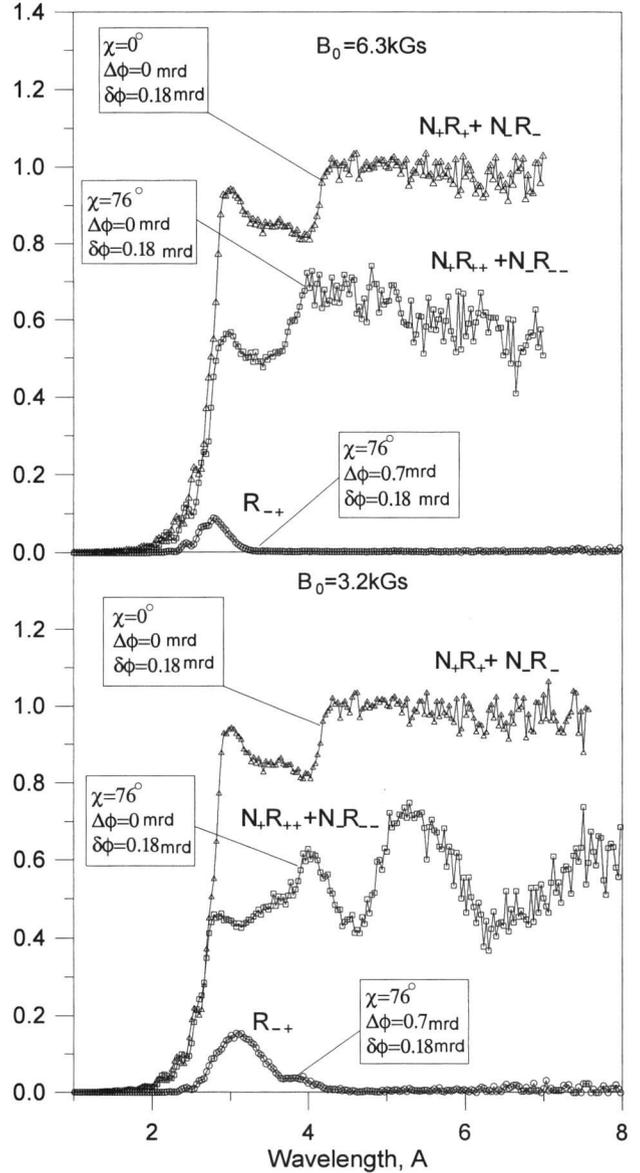


Fig.4 The wavelength dependence of  $N_+R_+ + N_-R_-$  in the specular direction  $\phi = \phi_0$  for  $\chi=0$  and  $\chi=76^\circ$ , and of  $|R_{-+}|^2$  in the off-specular direction ( $\Delta\phi=0.7$  mrad.): a)  $B=6.3$  kGs; b)  $B=3.2$  kGs.

It is easy to estimate the intensity of reflected beams in the case when the inside field is strong enough to make  $k^-$  imaginary, and leave  $k^+$  real. In the first approximation with respect to  $B_0/k^2$ , the denominator can be replaced by 1 and the intensity of the off-specular beam becomes proportional to

$$|R_{-+}|^2 = k^2 \left| \frac{-(k^{1-} - k^{1+})}{(k^+ + k^{1+})(k^- + k^{1-})} \sin \chi \right|^2 = \frac{\gamma B_1 \sin^2 \chi}{2(u + B_1)},$$

where  $\gamma \approx |2k/(k+k^{1+})|^2 \approx 1$ .

#### §.4 Experiment

The experiment was performed with the time-of-flight reflectometer of polarized neutrons at the IBR-2 reactor in Dubna.

The sample was a thin anisotropic FeCo film on a glass substrate. The external field was applied either parallel to the anisotropy axis in the film plane ( $\chi = 0$ ) or at an angle of  $76$  deg. to it (out of plane). The magnitude of the external

field could be varied in the range 0.01–7 kGs. The polarized neutron beam with a wide Maxwellian spectrum was incident on the film at a grazing angle  $\phi_0=4.2$  mrad. The polarization of the beam  $P(\lambda)$  was a monotonous function decreasing from  $P=0.98$  at  $\lambda=1.8$  Å to  $P=0.5$  at  $\lambda=7$  Å. The detector with a cadmium slit of 0.5 mm width was placed at 2.68 m from the sample. Thus, the angular aperture of the detector was  $\delta\phi=0.18$  mrad. To determine the reflection coefficients the intensity of the incident and reflected neutrons were measured at different orientations and magnitudes of the external field  $B$ .

For  $\chi=0$ , the dependence of  $N_+R_++NR_-$  on the wavelength was measured. Here,  $N_{\pm}(\lambda)$  are proportional to the intensities of the incident neutrons with two spin projections on the external field, and  $R_{\pm}$  are the squares of modules of the related reflection amplitudes.

For  $\chi=76^\circ$ , the angular distributions of the reflected neutrons were measured for two magnitudes of the external field: 0.2 and 6.3 kGs. (Fig. 3).

In the field  $B = 6.3$  kGs, off-specular neutrons were observed at  $\phi > \phi_0$ . To determine the dependence of  $\Delta\phi = \phi - \phi_0$  on  $\lambda$  the energy range of the counted neutrons was restricted to two intervals  $\Delta\lambda_1$  and  $\Delta\lambda_2$  around  $\lambda_1=2.6$  and  $\lambda_2=3.5$  Å, respectively. The measured ratio of the magnitudes  $\Delta\phi_1(\lambda_1)$  and  $\Delta\phi_2(\lambda_2)$  (Fig 3b) satisfies the relation  $\Delta\phi_1(\lambda_1)/\Delta\phi_2(\lambda_2) = (\lambda_1/\lambda_2)^2$  with a precision better than 0.5%, and corroborates the quadratic dependence of  $\Delta\phi$  on  $\lambda$ . The measurements of  $\Delta\phi$  at fixed  $\lambda$  and different  $B$  corroborate the linear dependence  $\Delta\phi \propto B$ .

For the fixed position of the detector at  $\Delta\phi=0.7$  mrad and two magnitudes of the external field:  $B=6.3$  and  $3.2$  kGs the spectral dependence of the square modules of  $R_{++}$ ,  $R_{+-}$ , and  $R_{-+}$  were measured (Fig. 4). The spectral interval of the measurements was determined by the angular detector aperture  $\delta\phi=0.18$  mrad.

The probabilities  $|R_{\pm\mp}(\lambda)|^2$  were also measured at  $\Delta\phi = 1.06$  mrad for two magnitudes of the external magnetic field (Fig. 5). The positions and spectral widths of the functions  $|R_{\pm\mp}(\lambda)|^2$  corroborate the expected theoretical dependence  $\Delta\phi \propto B\lambda^2$ . It is evident that the measurement of the nondiagonal elements  $|R_{\pm\mp}(\lambda)|^2$  in a wide spectral interval of  $\lambda$  in the off-specular direction requires detectors with a wide angular aperture, contrarily to the measurement of the sum  $N_+R_+(\lambda)+NR_-(\lambda)$  in the specular direction.

### §.5 Conclusion

The obtained experimental data demonstrate that the reflectometry in high external fields ( $B \geq 2$  kGs) from noncollinear structures with nondiagonal reflection matrices reveals strong angular dispersion of the reflected neutrons with reversed spins. For the case of a nonpolarized incident beam the observation of this dispersion gives the opportunity to measure the nondiagonal elements  $|R_{\pm\mp}(\lambda)|^2$  in the off-specular beams and the sum  $N_+R_+(\lambda)+NR_-(\lambda)$  in the specular one. It also gives the opportunity to get information on the distribution of magnetization in films using nonpolarized neutrons.

### Acknowledgments

One of the authors (V.K.I.) wants to express his gratitude to I.Carron for his invaluable assistance.

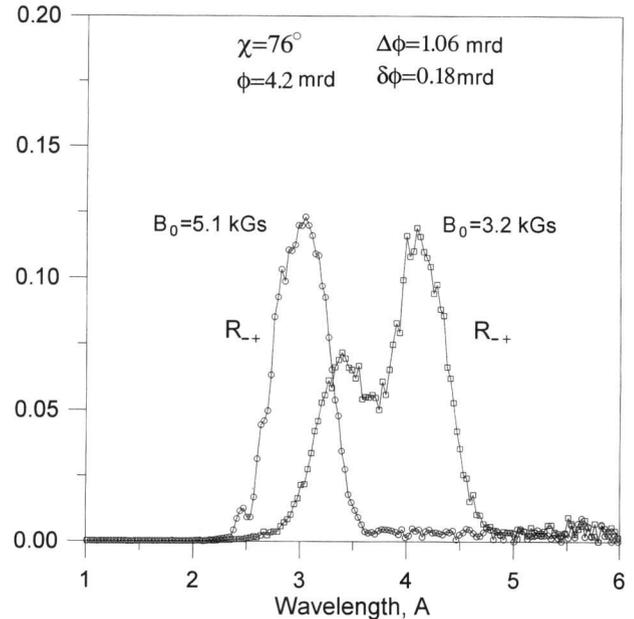


Fig. 5 The dependence of  $|R_{+-}|^2$  on  $\lambda$  for  $\Delta\phi=1.06$  mrad and two fields:  $B=5.1$  kGs, and  $B=3.2$  kGs. The shift and broadening of the spectral interval for the weaker field corroborate the dependence  $\Delta\phi \propto B\lambda^2$ . The bell shaped forms of both spectra are related to the small aperture  $\delta\phi=0.18$  mrad of the detector.

- 1: Hughes D.J., Burgy M.T., *Phys. Rev.* 81 (1951) 498.
- 2: Felcher G.P., Hildeke R.O., Crawford R.K., Haumann J., Kleb R. and Ostrowski G. *Rev.Sci.Instr.* 58 (1987) 609.
- 3: Korneev D.A., Pasyuk V.V., Petrenko A.V., and Dokukin E.B., "Neutron reflectivity studies on superconducting, magnetic and absorbing thin films on the polarized neutron spectrometer at the pulsed reactor IBR-2" in H.Zabel, I.K.Robinson (Eds.) "Surface X-ray and neutron scattering" (Proceedings of the 2nd Int.Conf., Bad Honnef, Germany, June 25-28, 1991), Springer Proceedings in Physics 61, Springer -Verlag
- 4: Lauter H.J., Bland J.A.C., Bateson R.D., and Jonson A.D. "Magnetic properties of ultra thin Co/Ag films investigated by polarized neutron reflection" in H.Zabel, I.K.Robinson (Eds.) "Surface X-ray and neutron scattering" (Proceedings of the 2nd Int.Conf., Bad Honnef, Germany, June 25-28, 1991)
- 5: Endoh Y., "Neutron reflection studies on magnetic superlattice", in "Neutron Optics Devices and Applications", C.Majkrzak, J.Wood, Editors, *Proc. SPIE* 1738, 224-232 (1992)
- 6: Fitzimmons M.R., Smith G.S., Pynn R., Nastasi M.A., Burkell E. *Physica B* 198 (1994) 169.
- 7: Ignatovich V.K. *Pis'ma ZhETP* 28 (1978) 311 (see *Sov. JETP Lett.*).
- 8: Korneev D.A. *Poverkhnost* 2 (1989) 13 (in Russian).
- 9: Ignatovich V.K. "The Physics of Ultracold Neutrons" Clarendon Press, Oxford, 1990.
- 10: Majkrzak C.F. *Physica B* 173 (1991) 75.
- 11: Aksenov V.L., Korneev D.A. and Chernenko L.P. "Time-of-flight four-beam neutron reflectometer REFLEX at the high flux pulsed reactor IBR-2: some polarized neutron reflectometry applications." in *Neutron Optics Devices and Applications*, C.Majkrzak, J.Wood, Editors, *Proc. SPIE* 1738, 335-345 (1992)
- 12: Korneev D.A., Chernenko L.P. "Neutron diffraction optics of films with noncollinear magnetic depth structure" in *Neutron Optics Devices and Applications*, C.Majkrzak, J.Wood, Editors, *Proc. SPIE* 1738, 468 (1992)
- 13: Zabel H. *Physica B* 198 (1994) 156.